

Room Temperature Magnetically Ordered Polar Corundum GaFeO₃ Displaying Magnetoelectric Coupling

Hongjun Niu,[†] Michael J. Pitcher,[†] Alex J. Corkett,[†] Sanliang Ling,^{‡,§} Pranab Mandal,[†] Marco Zanella,[†] Karl Dawson,[§] Plamen Stamenov,^{||} Dmitry Batuk,^{⊥,§} Artem M. Abakumov,^{⊥,¶} Craig L. Bull,[¶] Ronald I. Smith,[¶] Claire A. Murray,[▽] Sarah J. Day,[▽] Ben Slater,[‡] Furio Cora,[‡] John B. Claridge,^{*,†} and Matthew J. Rosseinsky^{*,†,§}

[†]Department of Chemistry, University of Liverpool, Crown Street, Liverpool L69 7ZD, United Kingdom

[‡]Department of Chemistry, University College London, Gower Street, London WC1E 6BT, United Kingdom

[§]Centre for Materials and Structures, School of Engineering, University of Liverpool, Liverpool L69 3GH, United Kingdom

^{||}CRANN, Trinity College Dublin, College Green, Dublin 2, Republic of Ireland

[⊥]EMAT, University of Antwerp, Groenenborgerlaan 171, 2020 Antwerp, Belgium


[¶]Skoltech Center for Electrochemical Energy Storage, Skolkovo Institute of Science and Technology, 143026 Moscow, Russian Federation

[¶]ISIS Neutron and Muon Source, Science and Technology Facilities Council, Rutherford Appleton Laboratory, Harwell Oxford, Didcot, Oxfordshire OX11 0QX, United Kingdom

[▽]Diamond Light Source, Diamond House, Harwell Oxford, Didcot, Oxfordshire OX11 0DE, United Kingdom

S Supporting Information

ABSTRACT: The polar corundum structure type offers a route to new room temperature multiferroic materials, as the partial LiNbO₃-type cation ordering that breaks inversion symmetry may be combined with long-range magnetic ordering of high spin *d*⁵ cations above room temperature in the AFeO₃ system. We report the synthesis of a polar corundum GaFeO₃ by a high-pressure, high-temperature route and demonstrate that its polarity arises from partial LiNbO₃-type cation ordering by complementary use of neutron, X-ray, and electron diffraction methods. In situ neutron diffraction shows that the polar corundum forms directly from AlFeO₃-type GaFeO₃ under the synthesis conditions. The A³⁺/Fe³⁺ cations are shown to be more ordered in polar corundum GaFeO₃ than in isostructural ScFeO₃. This is explained by DFT calculations which indicate that the extent of ordering is dependent on the configurational entropy available to each system at the very different synthesis temperatures required to form their corundum structures. Polar corundum GaFeO₃ exhibits weak ferromagnetism at room temperature that arises from its Fe₂O₃-like magnetic ordering, which persists to a temperature of 408 K. We demonstrate that the polarity and magnetization are coupled in this system with a measured linear magnetoelectric coupling coefficient of 0.057 ps/m. Such coupling is a prerequisite for potential applications of polar corundum materials in multiferroic/magnetoelectric devices.

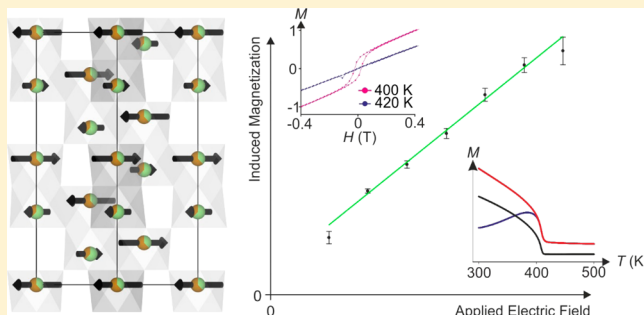

1. INTRODUCTION

New low-energy information storage and processing architectures have been proposed that rely on magnetoelectric and multiferroic materials,^{1,2} but the development of such systems is hampered by a paucity of suitable candidate materials, which must combine magnetic and polar electrical order at (or close to) room temperature. This is challenging because the electronic structure requirements for the two ground states are antagonistic in several respects, e.g., classical routes to polar materials rely on the coordination environments of closed shell *s*² and *d*⁰ cations, which are not consistent with magnetism.^{3–5}

The perovskite BiFeO₃ partially solves this problem by combining ferroelectrically and antiferromagnetically ordered sublattices.^{6,7} Several new approaches centered on the ABO₃ perovskite family have emerged recently, such as strain-generated ferromagnetism in epitaxial thin films,^{8,9} magnetic percolation at morphotropic phase boundary compositions in bulk ceramics¹⁰ and symmetry engineering¹¹ in bulk¹² and thin film materials.¹³ However, the identification of other materials

Received: October 25, 2016

Published: December 24, 2016

families where the two ground states may coexist at ambient temperature is less developed. By using the connection between the polar LiNbO_3 structure and perovskite, we identified polar derivatives of corundum as a new class of ternary oxide AFeO_3 materials that support both magnetic order (from a sufficiently high concentration of Fe^{3+} cations) and electrical order (enabled by cation site ordering), which can be targeted by high-pressure synthesis methods.¹⁴ The polar corundum ScFeO_3 , the first compound of this type, is ordered magnetically above room temperature, and the limited extent of long-range cation site order is sufficient to break inversion symmetry, producing electrical polarity (more recently, LiNbO_3 -type polymorphs of $\text{Mn}_2\text{FeTaO}_6$ ¹⁵ and $\text{Zn}_2\text{FeTaO}_6$ ¹⁶ have been reported with low magnetic ordering temperatures by a similar synthetic approach, and potential ferroelectric switching mechanisms have been investigated computationally¹⁷). The crystal chemistry of ScFeO_3 is complex as, in addition to the competition between bixbyite and partially ordered corundum phases,¹⁴ higher synthesis pressures stabilize a perovskite phase from which a fully ordered LiNbO_3 -type polymorph (with a correspondingly enhanced spontaneous polarization and Néel temperature) is recovered upon decompression.¹⁸ This implies that the structural chemistry of analogous AFeO_3 compositions (where *A* is a trivalent cation capable of adopting octahedral coordination) could offer polarity and magnetism if synthesized under appropriate conditions.

The ternary ferrite GaFeO_3 represents one such candidate for isolation of a polar corundum phase. Whereas at ambient pressure ScFeO_3 adopts the fluorite-derived bixbyite structure with Sc^{3+} and Fe^{3+} coordinated in an edge-sharing network of distorted MO_6 octahedra,¹⁹ ambient pressure GaFeO_3 adopts the polar orthorhombic AlFeO_3 structure with edge-sharing chains of $(\text{Ga}, \text{Fe})\text{O}_6$ octahedra and vertex-linked GaO_4 tetrahedra, but only exhibits long-range magnetic ordering and magnetoelectric coupling well below room temperature.^{20–23} Like ScFeO_3 and InFeO_3 ,²⁴ its structural behavior at high pressures and temperatures shows a complex interplay between corundum and perovskite structures: at ambient temperature, hydrostatic compression to pressures above 40 GPa converts the structure directly to an orthorhombic perovskite, which in turn transforms upon decompression to 25 GPa to a corundum-type phase that is retained down to ambient pressure.²⁵ Corundum-type GaFeO_3 can also be obtained directly by annealing at a sufficiently high temperature and pressure,²⁶ and by analogy with ScFeO_3 , it is possible that a polar variant of this structure will be accessible in this part of the phase diagram. We have targeted and isolated such a polar corundum GaFeO_3 phase, demonstrating that a family of materials adopt this structure. Polar corundum GaFeO_3 exhibits weak ferromagnetism above room temperature, and the extent of the cation site order is enhanced with respect to that observed in ScFeO_3 , allowing the measurement of linear magnetoelectric coupling consistent with the polar *R3c* space symmetry and the observed $\alpha\text{-Fe}_2\text{O}_3$ -like magnetic order.

2. EXPERIMENTAL DETAILS

Synthesis. Initially, the ambient pressure phase of GaFeO_3 was prepared from stoichiometric mixtures of Ga_2O_3 (99.999%) and Fe_2O_3 (99.998%) reacted at 900 °C for 12 h, 1300 °C for 24 h, followed by 1400 °C for 2 h in an alumina crucible in air. This precursor phase was then annealed under flowing oxygen at 1300 °C for 10 h to maximize the resistivity of the subsequent high-pressure product. The GaFeO_3 starting materials were then heated to 150, 500, 700, 900, 1100, 1300,

and 1500 °C, respectively, for 10 min at 6 GPa in a Pt-lined alumina crucible encapsulated within a graphite furnace in a Walker-type multianvil press. The samples were then cooled to room temperature, and the pressure was released. The high-pressure phase forming at 900 °C was used for structural, electric, and magnetic studies.

Powder X-ray Diffraction. Phase identification was performed using a PANalytical X'Pert Pro diffractometer in Bragg–Brentano geometry with monochromated $\text{Co K}\alpha_1$ radiation ($\lambda = 1.78896$ Å). Synchrotron XRD data (SXR) were collected from the I11 powder diffractometer (Diamond Light Source, UK). The sample was loaded inside a 0.1 mm quartz capillary, and data were collected using an incident wavelength $\lambda = 0.827127(1)$ Å over a 2θ range $2\text{--}150^\circ$ using high-resolution MAC detectors. Anomalous scattering data were collected on beamline I11 from a sample loaded onto the external surface of a 0.3 mm borosilicate capillary. A monochromator scan was used to measure the Ga K edge fluorescence spectrum, and an energy of 10.359 keV ($\lambda = 1.196901(5)$ Å) was selected for the anomalous scattering data set using the high-resolution MAC detectors. A corresponding nonanomalous data set was then collected from the same capillary at $\lambda = 0.826185(5)$ Å.

Powder Neutron Diffraction. Time-of-flight neutron powder diffraction (NPD) data were collected at ambient temperature and pressure on the POLARIS diffractometer at the ISIS facility, Rutherford Appleton Laboratory (UK). The sample was contained in a quartz capillary of diameter 1.5 mm and filled to a height of 40 mm. The data analysis was performed by Rietveld refinement using Topas Academic (version 5).

In Situ Powder Neutron Diffraction. High-pressure, high-temperature data were collected on the medium-resolution high-flux PEARL diffractometer (ISIS, UK) using a Paris–Edinburgh (PE) press.²⁷ The sample was pelletized and placed in a high-pressure furnace assembly.²⁸ The furnace assembly was placed between WC anvils in a V4 variant PE press dedicated to high-temperature pressure measurements. The sample pressure was determined by the equation of state (EoS) of platinum.²⁹ The temperature was determined by the resonance technique from the Hf foils included in the sample volume.³⁰ Time of flight data were collected using the 90° detector bank over a *d*-spacing range of 0.5–4 Å and corrected for anvil attenuation using in-house routines.²⁷ The hydraulic load of the press was gradually increased until the desired sample pressure was achieved prior to heating. The data analysis was performed by Rietveld refinement using Topas Academic (version 5).

SQUID Magnetometry. Magnetic measurements were carried out on powder samples using a commercial superconducting quantum interference device (SQUID) magnetometer MPMS XL-7 and MPMS3 (Quantum Design, USA). Magnetization data were recorded from 5 to 900 K in the following modes: ZFC (zero field cooling), FC (field cooling), and TRM (thermoremanent magnetization). The magnetic field-dependent magnetization was also measured at 10, 200, 400, and 420 K between -9 and 9 kOe.

Magnetoelectric Coupling. For magnetoelectric (ME) measurements, the polar corundum sample was polished to a $5\text{ }\mu\text{m}$ finish using SiC paper in a semiautomatic polishing machine. Ohmic contacts were made via sputtering Pt. ME measurements were carried out on a modified SQUID magnetometer.³¹ Prior to the measurements, the sample was poled in the following sequence: slowly cooled ($1\text{--}2$ K/min) from 350 to 130 K in a 20 kOe magnetic field and zero electric field (short circuit). At 100 K, an electric field of 350–400 kV/m was applied while cooling in the same magnetic field to the measurement temperature at 1 K/min. After poling, electric and magnetic fields were switched off, and electrodes were short circuited for 15 min.

Dielectric Constant. Dielectric properties were measured using an Agilent 4980 precision LCR meter for frequencies of 20 Hz to 2 MHz in the temperature range of 30–500 °C. A ramp rate of $1\text{ }^\circ\text{C min}^{-1}$ was used. The sample with sputter-coated Pt electrodes on both sides was loaded in a homemade sample holder, and data were collected using the LABVIEW program.

Differential Scanning Calorimetry (DSC). Heat flow was measured from a powder sample in an aluminum pan between room

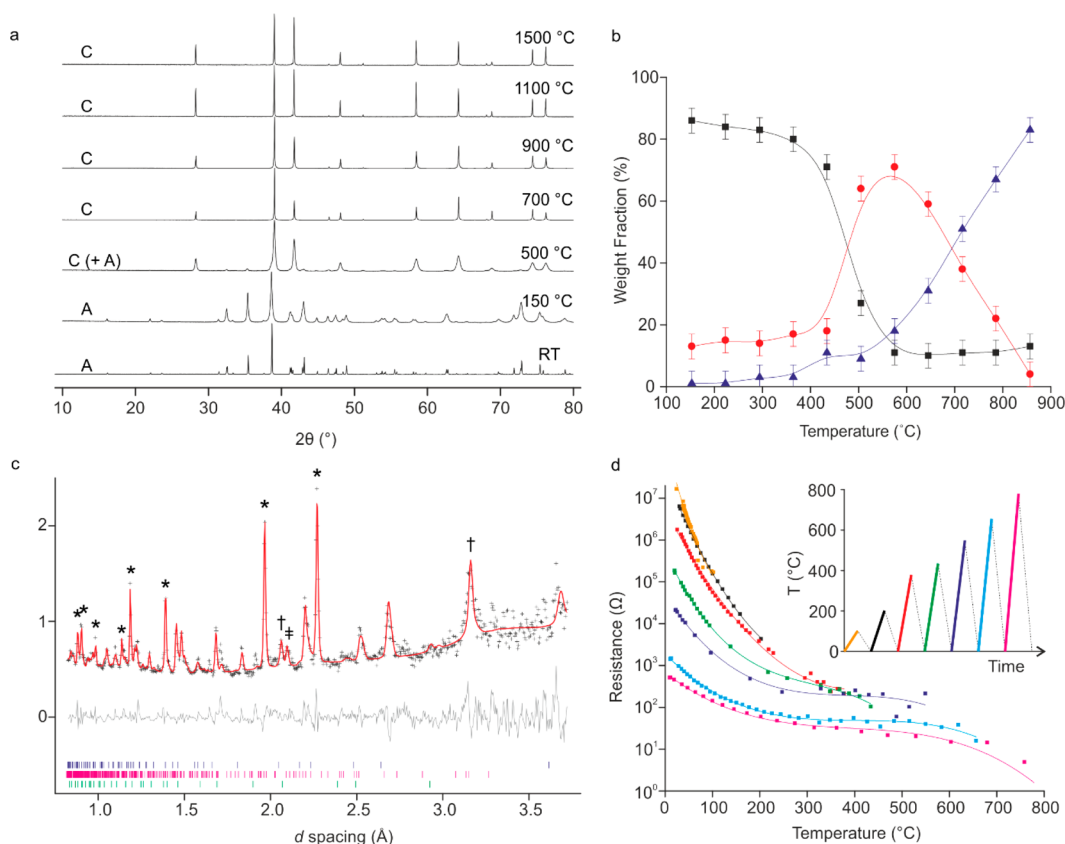


Figure 1. Formation of the corundum phase by high-temperature, high-pressure annealing. (a) Laboratory PXRD patterns obtained from GaFeO₃ quenched from a range of temperatures after annealing at 6 GPa. Patterns labeled A contain the starting AlFeO₃-structured phase, and those labeled C contain the corundum phase. (b) Refined weight fraction of the AlFeO₃ (black), corundum (red) phases, and spinel decomposition phase (blue) as a function of temperature at 4.7 GPa from in situ neutron diffraction. (c) Rietveld fit to in situ neutron data collected at 4.7 GPa and 500 °C. Blue tick marks = corundum phase; magenta = AlFeO₃ phase; green = spinel phase. Asterisks (*) mark peaks from the Pt pressure calibrant; daggers (†) mark graphite peaks, and the double dagger (‡) marks a vanadium peak. (d) In situ resistance measurements collected from a pellet of GaFeO₃ at 6 GPa cycled to increasing temperatures. Lines are a guide to the eye. The colors of the points correspond to their position in the heating sequence, which is shown in the inset.

temperature and 500 °C by the modulated DSC technique using a DSC Q2000 instrument (TA Instruments).

In Situ Resistance. Two-probe dc electrical resistance measurements as a function of temperature at 6 GPa were carried out using a Keithley 220 programmable current source and Keithley 2182 Nanovoltmeter. The GaFeO₃ powder was loaded into the alumina crucible, and Pt plates were employed on both the top and bottom of the crucible as the electrodes.

ICP-OES Measurements. Powder samples of GaFeO₃ (~50 mg) were dissolved in 10 cm³ of HF-HCl mixture (UniSolv Acid Dissolution Reagent 1, Inorganic Ventures) with 10 drops of concentrated HNO₃. The solution was then neutralized with 50 cm³ of triethanolamine-triethylenetetramine solution (UNS-1 solution, Inorganic Ventures) and diluted to approximately 20 ppm. The same protocol was used to prepare a standard solution from a stoichiometric mixture of Ga₂O₃ and Fe₂O₃. Measurements were collected on a Spectro Ciros Vision ICP-OES instrument.

TEM-EDX. EDX measurements were performed on a Jeol 2000FX using an EDAX EDX detector. Sample powder was dispersed in 500 μL of ethanol, and a drop of the suspension was dropped on a carbon-coated TEM copper grid. EDX spectra were collected for several minutes to obtain a suitable signal-to-noise ratio. Compositions were calculated from the mean of 25 particles.

Convergent Beam Electron Diffraction (CBED). Specimens were prepared using an FEI Helios 600i focused (Ga) ion beam instrument. Thin lamellae were sectioned and mounted on Cu grids using the lift out technique. Primary milling was performed using an acceleration voltage of 30 kV; final cleaning passes were applied to

specimen surfaces using a low energy (5 kV) polish. CBED experiments were performed in a JEOL 2000FX microscope operated at 200 keV.

Selected-Area Electron Diffraction (SAED) and High-Angle Annular Dark Field Scanning TEM (HAADF-STEM). TEM specimens were prepared by grinding the powder sample under ethanol and depositing several drops of the dispersion onto holey carbon grids. The SAED patterns were recorded using a Tecnai G2 microscope operated at 200 kV. The Fe and Ga distribution in the structure was investigated using HAADF-STEM imaging. The experiment was conducted on a probe aberration-corrected Titan 80-300 microscope operated at 300 kV. Theoretical HAADF-STEM images were calculated using QSTEM 2.20 software.

Mössbauer Spectroscopy. Mössbauer spectroscopy was performed in absorption, at room temperature, using a WissEl (MA-260) electromagnetic Doppler drive system, ⁵⁷Co(Rh) gamma source of actual activity of ~40 mCi, and a Xe gas Reuter-Stokes proportional counter. Canberra amplification, discrimination, and scaling electronics were used to acquire sample and α-Fe calibration spectra of width of 512 channels to a level of approximately 10⁷ counts per channel. Samples were diluted with sucrose (icing sugar) for measurements at an approximate ratio of 0.2 to prevent excessive line-shape distortion and nonresonant absorption. Custom folding, absorber geometry modeling, and nonlinear least-squares regression routines were used for the extraction of the spectroscopic parameters and their errors. Isomer shifts are referred to the source.

Computation. All calculations were performed under periodic boundary conditions using the CP2K^{32,33} code, which employs a

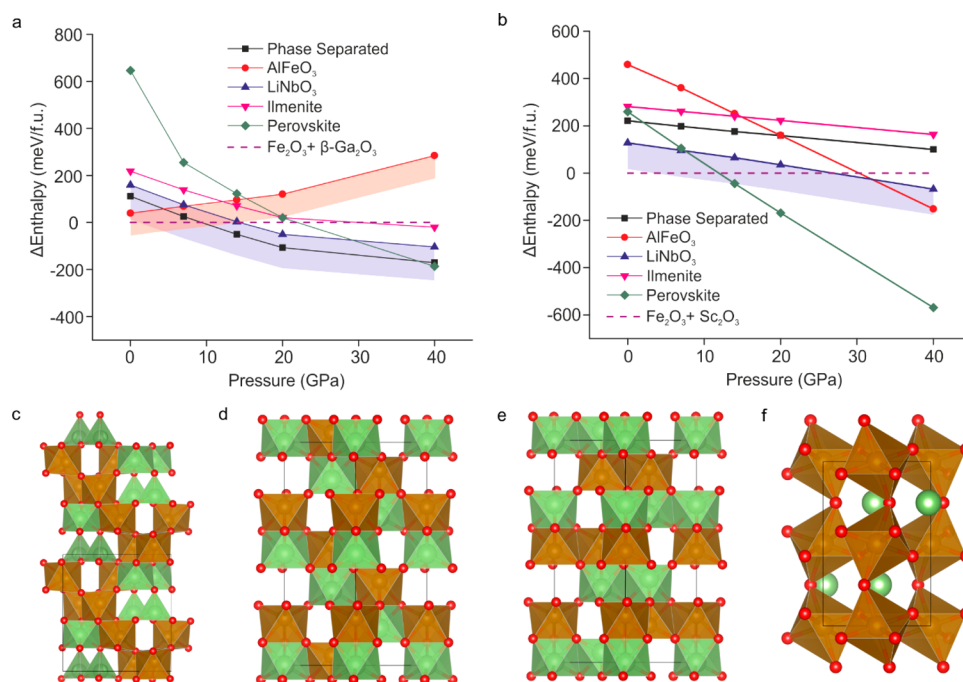


Figure 2. Calculated enthalpies as a function of pressure for (a) GaFeO₃ polymorphs in the AFM state and (b) ScFeO₃ polymorphs in the AFM state plotted relative to the binary oxides α -Fe₂O₃ + β -Ga₂O₃ and α -Fe₂O₃ + Sc₂O₃. The shaded areas represent an estimate of the configurational entropy of GaFeO₃ and ScFeO₃ at the respective synthesis temperatures of 1200 and 1800 K: 98.8 meV/f.u. for the ambient pressure AlFeO₃-type GaFeO₃, 143 meV/f.u. for corundum GaFeO₃, and 106 meV/f.u. for corundum ScFeO₃. (c) Ambient pressure AlFeO₃-type structure of GaFeO₃ viewed along [001], which features edge-sharing chains of (Fe, Ga) octahedra parallel to vertex-linked GaO₄ tetrahedra. (d) Polar LiNbO₃-type cation ordering in the corundum structure. (e) Nonpolar FeTiO₃ (ilmenite)-type cation ordering in the corundum structure. (f) Optimized *Pbnm* perovskite-type structure used for this calculation, which represents the phase that is accessible experimentally under applied pressures of 25 GPa.²⁵ Atom colors: green = Ga(Sc); brown = Fe; red = O.

mixed Gaussian/plane-wave basis set. We employed double- ζ polarization-quality Gaussian basis sets³⁴ and a 600 Ry plane-wave cutoff for the auxiliary grid in conjunction with Goedecker–Teter–Hutter pseudopotentials.^{35,36} Total energy calculations and structural optimizations, including both atomic coordinates and cell parameters, were performed at the hybrid density functional theory (DFT) level using the PBE0 exchange and correlation functional,^{37,38} which has 25% Hartree–Fock exchange (HFX). The HFX calculations were significantly accelerated by using the auxiliary density matrix method³⁹ and a truncated potential⁴⁰ with which the HFX energy becomes zero beyond a predefined real-space cutoff radius. For production quality calculations, we have used the cpFIT3 auxiliary basis sets, a cutoff radius of 4 Å, and a convergence threshold of 5.0×10^{-6} Ha for the self-consistent field cycle, and structural optimizations were considered to have converged when the maximum force on all atoms falls below 4.5×10^{-4} Ha Bohr⁻¹. Calculations were performed with the Γ -point approximation using a $2 \times 2 \times 1$ multiplication of the hexagonal primitive cell consisting of 120 atoms. Additional calculations in a $3 \times 3 \times 1$ supercell (270 atoms) show that the relative energy between FM and AFM magnetic configurations in the LiNbO₃ cation order converged to within 5 meV/f.u. in the $2 \times 2 \times 1$ supercell. A comprehensive and systematic configurational search on ScFeO₃ and GaFeO₃ in the corundum structure was performed as part of this study (described fully in the Supporting Information) in which the LiNbO₃ structure was identified as the ground state of corundum-type ScFeO₃. The ground state of corundum-type GaFeO₃ was found to be phase-separated layers of Fe₂O₃ and Ga₂O₃; hence, discussion of phase stability refers to LiNbO₃ and “phase separated” as the ground state references for ScFeO₃ and GaFeO₃, respectively. Additional details of the computational study, including defect formation energies, configurational search, and estimation of configurational entropies, are provided in the Supporting Information (including Figures S1–S3, and Tables S1 and S2).

3. RESULTS

3.1. Isolation and Stability of Corundum GaFeO₃

Extensive investigation of (T, P) synthesis conditions in the multianvil cell revealed a 700–900 °C temperature range at 6 GPa that afforded a diffraction pattern that could be indexed solely with a corundum unit cell after decompression and cooling to room temperature (Figure 1a). The composition was confirmed to be stoichiometric GaFeO₃ by ICP-OES measurements (Table S3) with a high level of compositional homogeneity confirmed by TEM-EDX (Figure S4). Reaction at higher temperatures produced Fe₃O₄ as a secondary phase in increasing quantity (2 wt % at 1100 °C, 19 wt % at 1500 °C) whereas 500 °C affords partial conversion of ambient pressure GaFeO₃ to the corundum structure. In situ neutron diffraction data collected at 4.7 GPa confirms that the ambient pressure orthorhombic GaFeO₃ is converted directly to a corundum-type phase (Figure 1b, c). Higher-resolution information on the transformation temperature is provided by in situ measurement of dc resistance under the synthesis conditions: by cycling a sample to increasing maximum temperatures, its resistance was found to decrease irreversibly during cycles to 400 and 550 °C, signifying the onset of the phase transformation before returning to near-reversible behavior for cycles to 650 and 800 °C, consistent with completed formation of the corundum phase (Figure 1d). A second sample was cycled four times between ~25 and 900 °C and showed an irreversible decrease in resistance on the first cycle, which coincides with the resistivity of subsequent cycles at 550 °C (Figure S5), implying that complete conversion to the corundum is achieved at this temperature. This is consistent with both the ex situ PXRD,

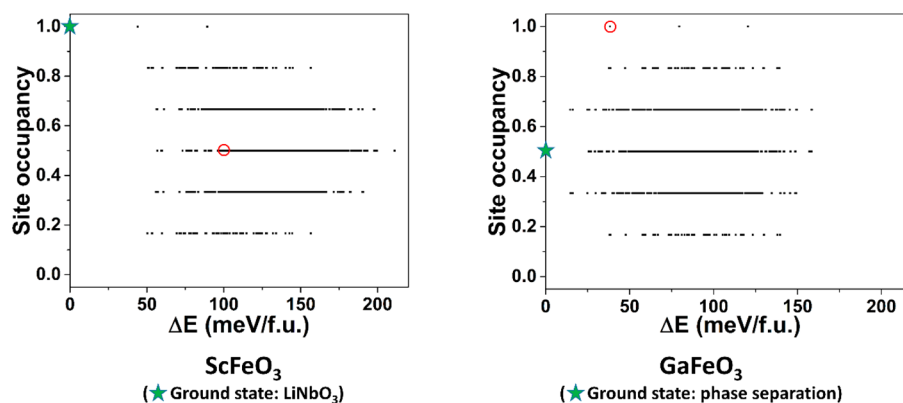


Figure 3. Calculated stabilities of different cation configurations in a hexagonal corundum-type unit cell. Site occupancies (defined as the proportion of Fe^{3+} cations in a given configuration that are coincident with Fe^{3+} positions in the fully ordered LiNbO_3 structure) of different configurations are plotted against their relative energies with respect to the ground state of ScFeO_3 (left) and GaFeO_3 (right). The phase-separated structure of ScFeO_3 and the LiNbO_3 -type GaFeO_3 are highlighted in red circles. The lowest energy configuration is marked with a green star.

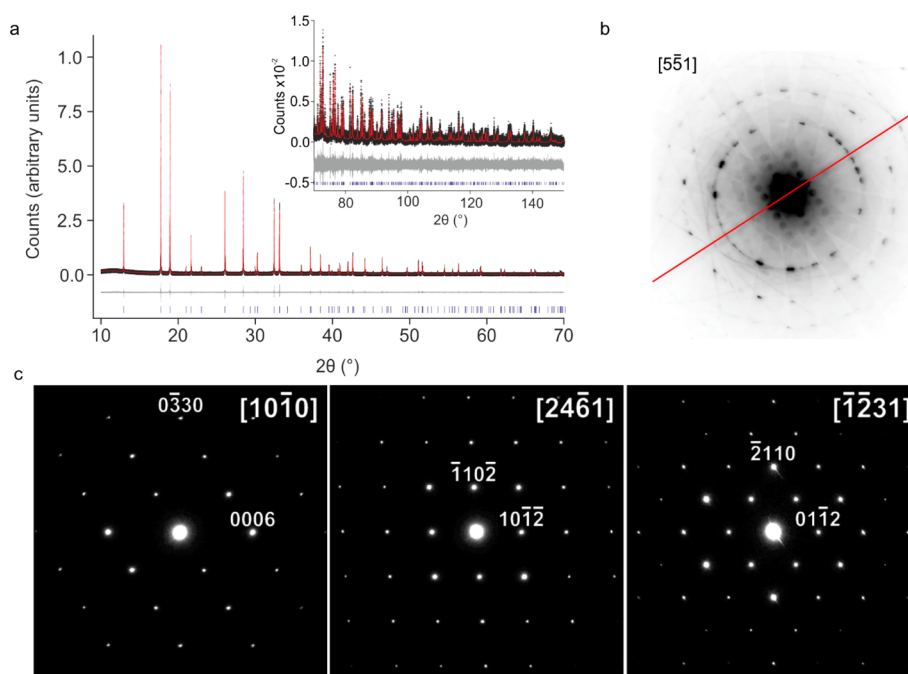


Figure 4. Unit cell and space group determination. (a) LeBail fit to SXRD data ($\lambda = 0.8256185 \text{ \AA}$) of corundum GaFeO_3 in the hexagonal setting of space group $R\bar{3}c$, which has the highest symmetry consistent with the systematic absences, yields a refined unit cell of dimensions $a = 5.01959(3) \text{ \AA}$ and $c = 13.5907(2) \text{ \AA}$. The fit to high angle data ($70 < 2\theta < 150^\circ$) is inset. Black markers = y_{obs} ; red line = y_{calc} ; gray line = $y_{\text{obs}} - y_{\text{calc}}$; blue tick marks = allowed hkl reflections. (b) CBED $[551]$ zone axis pattern of corundum GaFeO_3 , which contains a mirror plane as the only symmetry element, consistent with space group $R\bar{3}c$. (c) SAED patterns from three different zone axes, confirming the rhombohedral cell and systematic absences observed by SXRD.

where the pattern is already dominated by the corundum phase at 500°C , and the in situ NPD, where the refined AlFeO_3 -phase content reaches a minimum plateau at 575°C .

To better understand the isolation of polar corundum GaFeO_3 under high-pressure reaction conditions, we calculated the enthalpies of different polymorphs of GaFeO_3 at different pressures up to 40 GPa. We considered the ambient pressure AlFeO_3 -type structure, an orthorhombic perovskite structure, the LiNbO_3 and ilmenite ordered corundum structures, and the ground state corundum configuration produced by our configurational search (in which Ga and Fe form a structure with distinct $[001]$ blocks at either end of the corundum cell; see Supporting Information and Figure S1). Their enthalpies were compared with those of the binary oxides using the

ambient pressure forms $\alpha\text{-Fe}_2\text{O}_3$ and $\beta\text{-Ga}_2\text{O}_3$ as the references. Finally, an estimate of the configurational entropies available to the AlFeO_3 - and LiNbO_3 -type structures was calculated at 1200 K (see Supplementary Text). The calculated enthalpies as a function of pressure are plotted in Figure 2a with the estimated entropic contribution to the total energy at 1200 K overlaid for these two structure types to illustrate the estimated extent of entropic stabilization. The equivalent calculations for the same polymorphs of ScFeO_3 , using $\alpha\text{-Fe}_2\text{O}_3$ and bixbyite-type Sc_2O_3 as the references, are shown in Figure 2b.

For GaFeO_3 , the ambient pressure AlFeO_3 structure is the most stable ternary phase at 0 GPa and is stable relative to the binaries when configurational entropy of 98.8 meV/f.u. at 1200 K is considered. At this pressure, the LiNbO_3 structure is

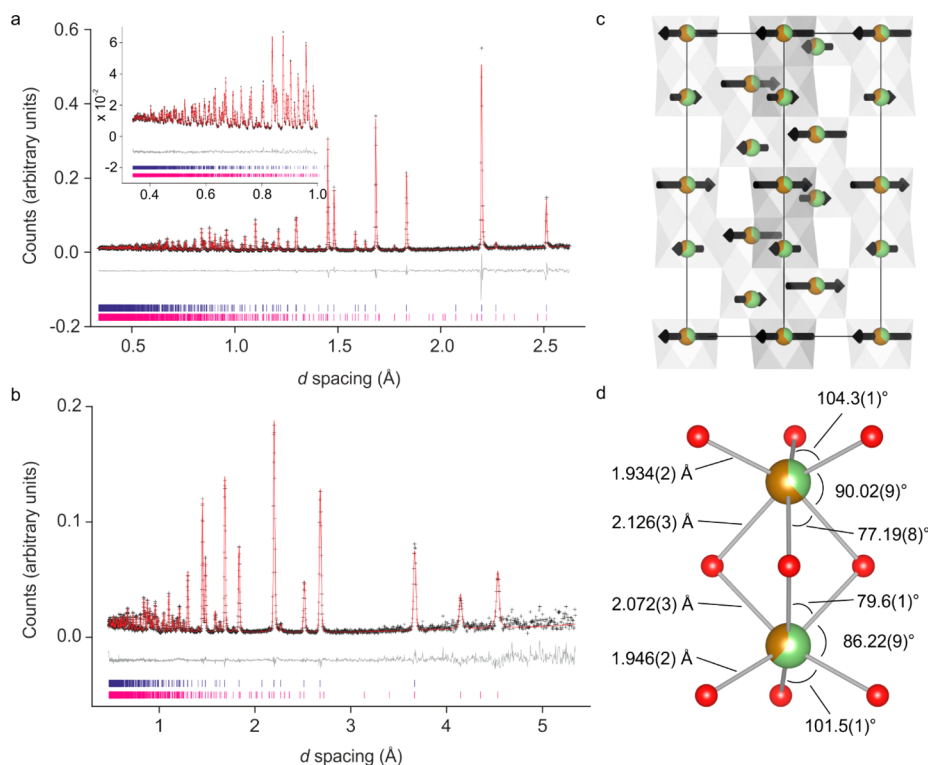


Figure 5. Refined polar corundum structure of GaFeO_3 . (a) Rietveld refinement against NPD data from the Polaris backscattering bank (inset: fit to the low d -spacing region) and (b) against Polaris bank 3 ($2\theta = 52.2^\circ$), which features two intense peaks of magnetic origin in the range $4 < d < 5$ Å. Black markers = y_{obs} ; red line = y_{calc} ; gray line = $y_{\text{obs}} - y_{\text{calc}}$; blue tick marks = nuclear structure; magenta tick marks = magnetic structure. (c) Refined nuclear and magnetic structure of GaFeO_3 viewed along 110. At each atom, green segments indicate Ga occupancy, brown segments indicate Fe occupancy, and black arrows indicate magnetic moments that are ordered parallel to the a axis in an antiferromagnetic arrangement. The magnitudes of the ordered moments are indicated by the sizes of the arrows. (d) Local coordination environments of the two crystallographically independent cation sites, which occupy adjacent face-sharing octahedra. The colors indicate the extent of occupancy by Fe (brown) and Ga (green).

unstable with respect to its binary constituents by 159 meV/f.u. at 0 K. With increasing pressure, the AlFeO_3 structure is progressively destabilized, and the corundum-type structures become the most stable beyond ~ 3 GPa. Among the corundum-type structures, the LiNbO_3 cation ordering is found to be more stable than the ilmenite ordering at all pressures. At ~ 30 GPa, the perovskite structure becomes more stable than the LiNbO_3 structure, which is in good agreement with previous experimental work.²⁵ In ScFeO_3 , the LiNbO_3 structure is the most stable ternary phase at 0 GPa but is less stable than the binary mixture by 128 meV/f.u.; the orthorhombic perovskite phase is stabilized more rapidly with pressure and becomes the most enthalpically stable phase at ~ 7 GPa.

These results show that configurational entropy due to disorder of Ga and Fe cations in the AlFeO_3 and corundum lattices at the synthesis temperatures plays a critical role in the stabilization of the ternary phases. This is consistent with our configurational search of corundum-type GaFeO_3 (see Figure 3), where a total of 151 configurations, including the fully ordered LiNbO_3 structure, are found within 50 meV/f.u. (~ 0.5 kT at the synthesis temperature of 1200 K) of the lowest energy configuration. These may correspond to states that are accessible under the synthesis temperature. This contrasts with ScFeO_3 , which has only 5 configurations within 50 meV/f.u. of the fully ordered LiNbO_3 ground state (Figure 3), indicating that a higher temperature is required to entropically stabilize the corundum structure of ScFeO_3 by accessing a greater number of configurations.

3.2. Structural Analysis. The synchrotron powder X-ray diffraction (SXRD) patterns of GaFeO_3 synthesized at high pressure could be indexed to an R -centered hexagonal unit cell with lattice parameters $a = 5.01936(4)$ Å and $c = 13.5903(1)$ Å as shown in Figure 4a, which is consistent with the corundum structure adopted by $\alpha\text{-Fe}_2\text{O}_3$.^{41,42} The observed reflection conditions (hkl : $h + l = 3n$, $l = 2n$), also observed in selected-area electron diffraction (SAED) patterns (Figure 4c), are consistent with $R3c$ and $\bar{R}3c$ space groups that correspond to the polar LiNbO_3 and nonpolar (fully disordered) corundum structures, respectively. These systematic absences preclude the possibility of an ilmenite structure type with $\bar{R}3$ space group symmetry. Regarding the possible acentric $R3c$ and centrosymmetric $\bar{R}3c$ structural models of GaFeO_3 , the very similar X-ray scattering factors of Fe^{3+} and Ga^{3+} preclude unambiguous space group assignment from Rietveld refinement against PXRD data alone. We addressed this problem in two parts: first, by using convergent beam electron diffraction (CBED) to determine the point group of the GaFeO_3 corundum, and second by employing powder neutron diffraction and anomalous X-ray scattering to determine the extent of the cation ordering.

The whole pattern symmetry of the $[5\bar{5}1]$ zone from CBED (Figure 4b) displays only a single m symmetry element. Considering only trigonal crystal systems, this permits the assignment of the $3m$ point group,⁴³ and along with the observed reflection conditions from PXRD data, indicates that the high-pressure phase of GaFeO_3 crystallizes in the noncentrosymmetric $R3c$ space group. For confirming the assignment of the $R3c$ space group and investigating the degree

Table 1. Structural Parameters for R3c GaFeO₃ (Sample 1) from Rietveld Refinement against Room Temperature NPD Data with Refined Lattice Parameters $a = 5.01871(9)$ Å, $c = 13.5879(3)$ Å, and $V = 296.39(1)$ Å³

	x	y	z	$B_{\text{iso}}/\text{\AA}^2$	occ.	M/μ_B
Ga(1)	0	0	0	0.231(3)	0.32(2)	
Fe(1)	0	0	0	0.231(3)	0.68(2)	1.03(3)
Fe(2)	0	0	0.28919(5)	0.231(3)	0.32(2)	2.15(2)
Ga(2)	0	0	0.28919(5)	0.231(3)	0.68(2)	
O(1)	0.3026(2)	−0.0046(4)	0.8922(3)	0.284 (5)	1	

Table 2. Structural Parameters for R3c GaFeO₃ (Sample 2) Refined against Room Temperature NPD Data with Refined Lattice Parameters $a = 5.02547(9)$ Å, $c = 13.6057(3)$ Å, and $V = 297.31$ (2) Å³

	x	y	z	$B_{\text{iso}}/\text{\AA}^2$	occ.	M/μ_B
Ga(1)	0	0	0	0.216(4)	0.38(3)	
Fe(1)	0	0	0	0.216(4)	0.62(3)	1.08(4)
Fe(2)	0	0	0.28906(5)	0.216(4)	0.38(3)	2.00(3)
Ga(2)	0	0	0.28906(5)	0.216(4)	0.62(3)	
O(1)	0.3030(3)	−0.0033(5)	0.8916(2)	0.34(2)	1	

of cation order in GaFeO₃, neutron powder diffraction (NPD) analysis of two samples synthesized by the same protocol utilized the modest contrast in the neutron scattering lengths of Fe (9.45 fm) and Ga (7.288 fm). The appearance of Bragg peaks that were not present in the SXRD pattern, including two intense reflections at 4.14 and 4.54 Å, confirmed the presence of long-range magnetic order at room temperature. The magnetic structure was determined by representational analysis using the SARAH package⁴⁴ and was found to be a $k = 0$ G-type antiferromagnetic arrangement analogous to the high-temperature antiferromagnetic structure of α -Fe₂O₃⁴⁵ with spins aligned parallel to the a axis. Structural models in R3c (LiNbO₃) and R3c (corundum) were refined against four Polaris data banks simultaneously with the magnetic structure modeled in a P1 cell. In the disordered corundum (R3c) refinement, the magnitudes of the magnetic moments were constrained to a single refined value to reflect the statistical distribution of Fe³⁺ cations. In the cation-ordered model (R3c), the occupancies of Ga³⁺ and Fe³⁺ on each site in the nuclear phase were refined with a constraint on the total composition, and the magnetic phases were modeled with two independently refined moments whose positions in the P1 cell corresponded to the LiNbO₃-type cation ordering. In addition to site occupancy refinement in the LiNbO₃ model, atomic coordinates and isotropic thermal displacement parameters (B_{iso}) were refined with B_{iso} constrained to be equal for the Fe/Ga sites.

For both samples, the best goodness-of-fit was obtained from refinement in the R3c space group with R3c (disordered corundum) giving the higher χ^2 (see Tables S4 and S5). Inspection of the refined R3c model revealed that the refined cation occupancies from the nuclear scattering in R3c resulted in compositions of [Ga_{0.68(2)}Fe_{0.32(2)}][Ga_{0.32(2)}Fe_{0.68(2)}]O₃ (36(2) % ordered; defined by the difference in site occupancy) and [Ga_{0.62(3)}Fe_{0.38(3)}][Ga_{0.38(3)}Fe_{0.62(3)}]O₃ (24(3) % ordered) for the two samples, which is consistent with the relative magnitudes of the ordered spins on each site in the magnetic structure: the ordered moment at the Fe-rich site in sample 1 refined to 2.15(2) μ_B , whereas that of the Fe-poor site refined to 1.03(3) μ_B . Assuming that individual Fe have the same moment at each site, then the refined (average) moments are due to different populations of Fe at each site, which yields [Ga_{0.68(1)}Fe_{0.32(1)}][Ga_{0.32(1)}Fe_{0.68(1)}]O₃, and the equivalent

calculation for sample 2 yields [Ga_{0.65(1)}Fe_{0.35(1)}]-[Ga_{0.35(1)}Fe_{0.65(1)}]O₃. The Rietveld fits are shown together with the refined R3c model in Figure 5, and refined parameters for each sample are shown in Tables 1 and 2. The consistency between the extent of cation ordering obtained directly from the nuclear scattering and the extent of ordering obtained independently from the magnetic scattering, in addition to the superior goodness-of-fit, confirms the assignment of polar R3c symmetry. The polarization of GaFeO₃ (sample 1) was calculated as 6.9 $\mu\text{C cm}^{-2}$ from a formal point charge model using the program PSEUDO⁴⁶ with the refined atomic coordinates of sample 1.

Anomalous scattering synchrotron X-ray diffraction at the Ga K edge provides an alternative probe of the extent of cation order. The R3c model was refined simultaneously against two histograms and collected at ambient temperature at resonant (10.359 keV) and nonresonant (15.119 keV) energies from sample 1. The background was fitted by refinement of a Chebyshev polynomial function, and peak profiles were modeled by a Pearson VII function with a refined axial divergence correction. Lattice parameters, atomic coordinates, and isotropic thermal displacement parameters were refined independently for each site, and a Suortti surface roughness (absorption) correction was refined for each histogram. Initially, a series of [Ga _{x} Fe_{1- x}][Ga_{1- x} Fe _{x}]O₃ models with the extent of cation ordering (x) varying systematically between 0 $\leq x \leq 1$ were refined, and the resulting plot of χ^2 vs x (Figure S6) showed two shallow minima centered approximately at $x = 0.4$ and 0.6, consistent with the partial cation ordering observed by NPD. By allowing x to refine freely, a composition [Ga_{0.596(4)}Fe_{0.404(4)}][Ga_{0.404(4)}Fe_{0.596(4)}]O₃, which is 19.2(6) % ordered, was obtained, which is within four standard deviations of the NPD value (furthermore, the shallow minima in χ^2 vs x indicate that the reported least-squares errors on x from SXRD are underestimated). Both the NPD and SXRD results are also consistent with the computational screening of configurational entropy; the average cation order in the 2331 configurations examined and displayed in Figure 3, weighted by their relative population at 900 °C, yields a value of [Ga_{0.61}Fe_{0.39}]-[Ga_{0.39}Fe_{0.61}]O₃.

HAADF-STEM was used as a local probe to image the cation ordering directly. The two crystallographic positions jointly occupied by Fe and Ga form separate atomic columns in the

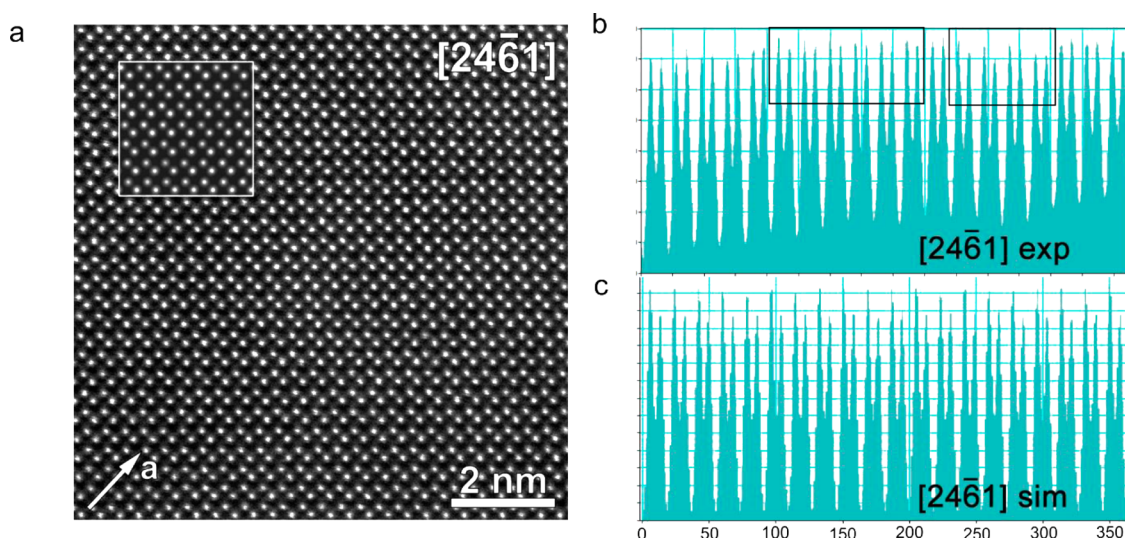


Figure 6. HAADF-STEM analysis of polar corundum GaFeO_3 . (a) Experimental HAADF-STEM image from the $[24\bar{6}1]$ axis with a simulated image (inset) generated from the refined (PND) crystal structure. (b) Intensity profiles measured from individual rows of atomic columns over large areas from the experimental image, and (c) intensity profiles measured over large areas from the simulated image. Regions in (b) that resemble the simulated structure of (c) are marked with black rectangles.

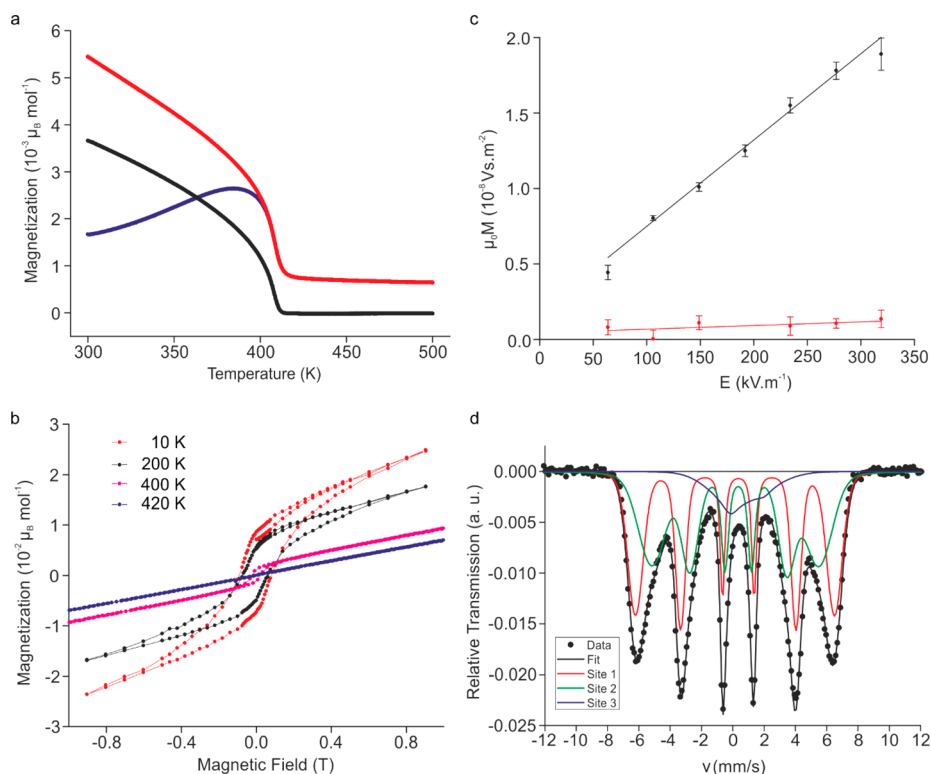


Figure 7. Magnetic properties of polar corundum GaFeO_3 . (a) Zero field cooled (blue points), field cooled (red points), and remanent (black) magnetization as a function of temperature in the range 300–500 K and measured with an applied field of 0.1 T. (b) Magnetization as a function of applied magnetic field at temperatures of 10 K (red points), 200 K (black points), 400 K (magenta points), and 420 K (blue points). (c) Induced ac magnetization versus applied ac electric field amplitude at 10 K for two samples: as-made (black points) and postannealed at 380 °C (red points). (d) ^{57}Fe Mössbauer spectrum at ambient temperature, showing hyperfine splitting consistent with long-range magnetic ordering and fitted with a three-site model (see Table 3 for fitted parameters).

structure as viewed along the $[24\bar{6}1]$ ($= \langle 100 \rangle_p$) direction (Figure S7). In HAADF-STEM, the observed intensity is proportional to the composition of the atomic columns and scales approximately as $Z^{1.6-1.9}$ (where Z is the average atomic number of the projected columns). Because of a very small difference between the average Z of the Fe- and Ga-rich atomic

columns ($Z = 27.6$ and 29.4 , respectively), the associated difference in brightness is expected to be subtle (see the calculated intensity profile in Figure 6c). Nevertheless, the intensity profiles taken from the experimental $[24\bar{6}1]$ HAADF-STEM image (Figure 6a, b) show systematic intensity differences reminiscent of that observed on the profile from

the calculated image (Figure 6c). All of these structural analyses confirm the $R3c$ space group with partial Ga/Fe order in the polar corundum structure.

3.3. Magnetic Order and Magnetoelectric Coupling. Mössbauer spectroscopy of polar corundum GaFeO_3 at ambient temperature and pressure confirms the long-range magnetic order demonstrated at room temperature by neutron diffraction (Figure 7d with fitted parameters shown in Table 3).

Table 3. Mössbauer Fitting Parameters for the Spectrum of Figure 7 with Errors Provided in Brackets

site	B_{hf} (T)	ΔB_{hf} (T)	IS (mm/s)	QS (mm/s)	A (%)
1	39.49(2)	0.28(1)	0.249(3)	0.21(1)	44.00(1)
2	33.11(2)	0.37(1)	0.257(3)	0.19(1)	47.09(1)
3	0	0	0.93(1)	2.16(3)	8.91(1)

The absorption pattern is clearly decomposed into a combination of two magnetically ordered sites with average hyperfine fields of 39.48 and 33.09 T, respectively (the larger of the two being close to that of Goethite⁴⁷ with its transition temperature of $\sim 400 \text{ K}$ ⁴⁸), which account for 91.09(2) % of the fitted area with the remainder assigned to one asymmetric paramagnetic doublet accounting for 8.91(2) % of the fitted area, which is a dynamic line shape resulting from the proximity of the Néel temperature. The two main sites exhibit significant static hyperfine field distributions with widths of 0.2–0.3 T. The fitted isomer shift (IS) of 0.25 mm/s and quadrupole splitting of 0.19 mm/s are consistent with Fe^{3+} , but the IS is smaller than expected for a typical octahedral coordination in an oxide, which may be due to the high degree of static disorder in the system. Isomer shifts of $<0.25 \text{ mm/s}$ have been reported under applied hydrostatic pressure for a corundum GaFeO_3 produced by transformation from the metastable perovskite (and thus likely to be highly ordered),²⁵ demonstrating a high degree of sensitivity of IS to the local coordination environment in this system.

Figure 7a shows the magnetization of polar corundum GaFeO_3 measured in an applied magnetic field of 1000 Oe in zero field cooled (ZFC), field cooled (FC), and thermomagnetic magnetization (TRM) from 300 to 500 K. ZFC/FC divergence appears at 408 K together with the onset of TRM. The $M(H)$ isotherms in Figure 7b are consistent with this magnetic ordering temperature of 408 K. The linear isotherm at 420 K shows that the sample is paramagnetic with hysteresis observed at and below 400 K, consistent with weak ferromagnetism occurring simultaneously with the antiferromagnetic order. ZFC, FC, and TRM magnetization data between 5 and 350 K (Figure S8) show that no magnetic transition occurs below 408 K. The remanent magnetization was $0.012 \mu_B/\text{f.u.}$ at 10 K (Figure 7b).

For spurious signals caused by leakage currents to be minimized, magnetoelectric measurements were carried out at 10 K on the polar corundum GaFeO_3 sample poled both electrically and magnetically (the resistivity at 10 K, measured in situ, was $2.38 \times 10^9 \Omega \text{ m}$). The ME susceptibility (α), measured as the slope of the induced ac magnetization (M_{ac}) relative to the applied ac electric field amplitude (E_{ac}) is 0.057 ps/m (Figure 7c). The observation of linear magnetoelectric coupling is consistent with the symmetry of the magnetic structure: above the Morin transition,⁴⁵ $\alpha\text{-Fe}_2\text{O}_3$ adopts $2/m$ magnetic point symmetry (which is centrosymmetric, permitting weak ferromagnetism but not linear magnetoelectric

coupling⁴⁹), but the cation ordering in polar corundum GaFeO_3 eliminates the inversion center, thus lowering the magnetic point symmetry to m ,⁵⁰ which permits both weak ferromagnetism and linear magnetoelectric coupling.⁴⁹ The observed magnitude of α is similar to that observed in other Fe-based polar magnetoelectrics that are ordered magnetically above room temperature.^{10,12,51} Demonstration of switchable electrical polarization (i.e., ferroelectricity and multiferroicity) was not possible in these samples due to the high dielectric loss.

3.4. Thermal Stability. For the thermal stability and decomposition behavior of polar corundum GaFeO_3 at ambient pressure to be tested, the as-made samples were annealed at different temperatures between 300 and 1000°C in air. Ex situ PXRD patterns of the postannealed samples showed that the orthorhombic ambient pressure phase is recovered after annealing at 1000°C , but the corundum unit cell is retained after annealing at $300\text{--}800^\circ\text{C}$ with no apparent decomposition (Figure S9). However, DSC and in situ dielectric measurements (Figure 8) collected on heating from 25 to 500°C show an endothermic peak and a corresponding peak in the dielectric constant, which is frequency independent (Figure S10) and centered at approximately 200°C . The feature is strongly pronounced during the first heating cycle and absent in subsequent cycles, which indicates the occurrence of an irreversible phase transition. For investigating whether this is associated with a loss of polarity in the sample, CBED images, magnetization, and magnetoelectric coupling data were collected on annealed samples.

Figure 7c shows that the ME susceptibility α decreases from 0.057 ps/m for as-made polar corundum GaFeO_3 to 0.003 ps/m for the sample annealed at 380°C : for this sample, the induced magnetic moment is below the detection limit of 10^{-9} emu . Close inspection of the CBED whole pattern symmetry for the $[\bar{1}11]$ zone axis (Figure S11) reveals the sample to have retained $3m$ point symmetry, which implies that the sample has retained some residual polarity. Taken together with the magnetoelectric measurements, this implies that the polarity of the material (via the cation ordering) is diminished but not eliminated entirely by annealing polar corundum GaFeO_3 at this temperature. The weak ferromagnetism, which arises from the $\alpha\text{-Fe}_2\text{O}_3$ -type magnetic structure, is also retained after thermal treatment (Figure S12). This is consistent with the $2/m$ magnetic point symmetry of $\alpha\text{-Fe}_2\text{O}_3$ above the Morin transition:⁴⁵ the loss of cation ordering in polar corundum GaFeO_3 would restore the inversion center, thus raising the magnetic point symmetry back to $2/m$ (which is centrosymmetric, permitting weak ferromagnetism but not linear magnetoelectric coupling⁴⁹).

4. DISCUSSION

Under the high-temperature, high-pressure conditions applied in this study, a corundum phase of GaFeO_3 forms directly from the ambient pressure phase in contrast to the sequence of phases observed upon application of pressure at room temperature in which a corundum phase is accessed via a nonquenchable perovskite phase.²⁵ The fact that the phase does not form by transformation from the high-pressure perovskite phase^{18,25} means that the extent of Ga/Fe ordering is limited, producing the polar corundum structure rather than the fully ordered LiNbO_3 structure. NPD and X-ray anomalous scattering experiments demonstrate a greater degree of ordering in GaFeO_3 than in the isostructural ScFeO_3 . Our computational results imply that GaFeO_3 should have a greater tendency

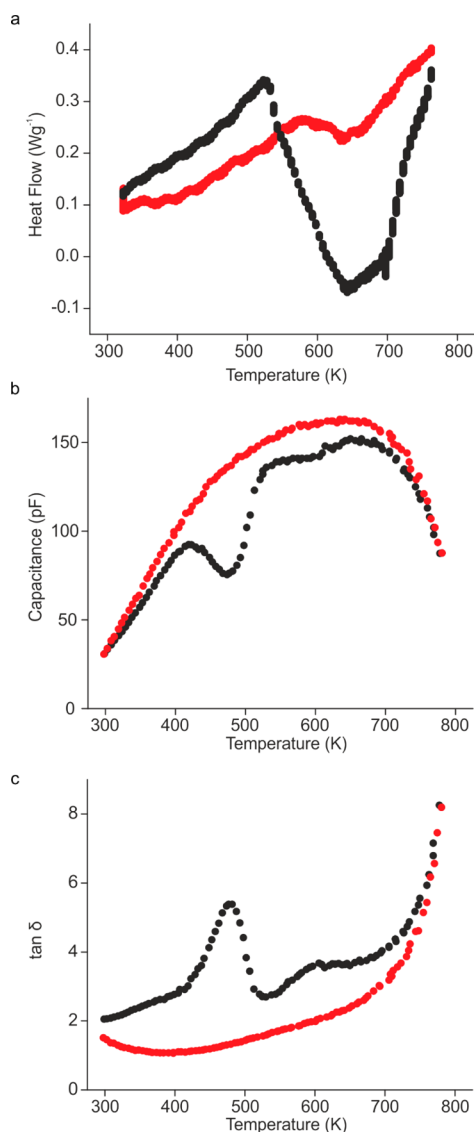


Figure 8. Calorimetric and dielectric behavior of polar corundum GaFeO₃ synthesized at 900 °C. (a) DSC scans performed on heating; black points represent the first cycle, and red points represent the second cycle. (b) Capacitance data recorded on the first heating cycle (black points) and second heating cycle (red points). (c) Dielectric loss recorded on first heating cycle (black points) and second heating cycle (red points).

toward cation disorder than ScFeO₃ at a given synthesis temperature, as demonstrated by the higher number of accessible cation configurations in GaFeO₃ (Figure 3). This originates from the small overall energy cost of Ga/Fe site swaps in GaFeO₃, whereas only the antisite Sc/Fe defect within face-shared dimers is energetically possible in ScFeO₃. Although the enthalpy of the polar corundum phase of both GaFeO₃ and ScFeO₃ is unstable relative to the binary oxides, the higher entropic content of GaFeO₃ (provided by the large number of thermally accessible cation configurations in the corundum cell at the synthesis temperature) means that its polar corundum phase is stabilized at a lower temperature than that of ScFeO₃. Experimentally, this results in polar corundum GaFeO₃ being stabilized at 900 °C, whereas polar corundum ScFeO₃ must be synthesized at a much higher temperature of 1400 °C. The effect of the different synthesis temperatures of

the two materials is expected to have an impact on the extent of cation ordering. From our previous Monte Carlo simulation of ScFeO₃,¹⁴ it was clear that, between 1300 and 1450 K, ScFeO₃ transformed from a mainly ordered to a mainly disordered structure. It is also clear that ScFeO₃ is calculated to be much more ordered than GaFeO₃ at 1200 K with a site occupancy of ~0.9. This indicates that the experimentally observed cation disorder in polar corundum ScFeO₃ is driven by the enhanced configurational entropy at the higher synthesis temperature. In GaFeO₃, the low synthesis temperature of 900 °C provides sufficient configurational entropy to stabilize the polar corundum, but it is insufficient to disorder the material to the same extent as seen for ScFeO₃ synthesized at 1400 °C and consequently produces more ordered compounds. We note the creation of antisite defects in LiNbO₃-type GaFeO₃ (e.g., by swapping cations in adjacent face-sharing MO₆ octahedra, as described in the Supporting Information) is less energetically demanding than in LiNbO₃-type ScFeO₃ (see Table S2), and the antisite defects may be partly responsible for the cation disorder in polar corundum GaFeO₃. It is possible that another source of disorder could originate from the precursor of corundum GaFeO₃, i.e., the ambient pressure AlFeO₃-type, in which the extent of cation ordering is dependent on the synthesis conditions⁵² and predicted from our simulation based on small energy costs of creating antisite defects (see Table S6). This implies that a more ordered polar corundum GaFeO₃ may be obtained from a highly ordered precursor, e.g., the fully ordered perovskite, as observed experimentally in ScFeO₃.¹⁸

In most respects, the refined crystal structure of GaFeO₃ is very similar to that of ScFeO₃. The unit cell volume of GaFeO₃ is approximately 10% smaller than that of ScFeO₃ on account of the smaller ionic radius of Ga³⁺ (0.62 Å) relative to that of Sc³⁺ (0.745 Å). This is an isotropic contraction driven by the smaller average size of the MO₆ coordination octahedra, as indicated by the similar *c/a* ratios in the two compounds (2.71 and 2.69, respectively). The unit cell dimensions of GaFeO₃ are very close to those of α-Fe₂O₃^{41,42} and are consistent with those reported from corundum-structured GaFeO₃ in a recent in situ high-pressure study.²⁵ The refined metal–oxygen distances, illustrated in Figure 5, lie in the range 1.93–2.13 Å, and the refined volume of the Ga-rich MO₆ polyhedron (10.49 Å³) is slightly smaller than that of the Fe-rich polyhedron (10.64 Å³), consistent with the relative ionic radii. As in the binary corundums and ScFeO₃, the cations are displaced from the centers of the face-sharing MO₆ octahedra by electrostatic repulsion.

Polar corundum GaFeO₃ exhibits weak ferromagnetism with an ordering temperature of 408 K; this is approximately 50 K higher than the ordering temperature observed in ScFeO₃,¹⁴ which may be due to its enhanced cation ordering. The remanent magnetization of GaFeO₃ (0.012 μ_B/f.u.) is comparable to that observed in ScFeO₃ (0.0106 μ_B/f.u.).¹⁴ The combination of weak ferromagnetism and absence of inversion symmetry permits magnetoelectric coupling in GaFeO₃. The observed linear magnetoelectric susceptibility (α) of 0.057 ps m⁻¹ is small in comparison to other Fe-based polar weak ferromagnetic ceramics,^{10,51} but the fact that the room temperature structure is identical to the structure at the measurement temperature (10 K) implies that, given the definition of a suitable processing protocol, magnetoelectric coupling may be attainable under ambient conditions in this compound. The magnitude of this coupling falls below a detectable value when the sample is heated to 380 °C at

ambient pressure. DSC and dielectric measurements suggest that this is due to an irreversible phase transition; CBED patterns, however, indicate that 3m point symmetry is still present in the sample. This indicates that the polarity of the sample (driven by the cation ordering that defines the polar corundum structure type) is degraded sufficiently to weaken the ME response below the detection limit but is not entirely eliminated by annealing under these conditions. Ultimately, the ambient pressure phase is recovered by annealing at a sufficiently high temperature.

5. CONCLUSIONS

GaFeO₃ is the second member of the polar corundum family and the first to display ME coupling. The enhanced cation site order in GaFeO₃ over ScFeO₃ confirms the distinction of this family both from nonpolar corundum and from fully LiNbO₃-ordered derivatives. The less extreme synthesis conditions required to access polar corundum indicate that a broad family of materials should be accessible, for example, through multiple cation decoration of corundum.

The magnetoelectric coupling shows that the engineered coexistence of magnetization and polarization in new structural families is a route to coupling these degrees of freedom; thin film growth, already achieved for ScFeO₃,¹⁴ is a route to tune this further. The relationship between M, α , and the cation site order is also controllable via site-ordering extent. The absence of measurable magnetic impurities under the optimized synthesis conditions is consistent with the stability and chemical robustness of this new family of room temperature polar magnetic magnetoelectric materials.

■ ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge on the ACS Publications website at DOI: 10.1021/jacs.6b11128.

Additional computational details and results, TEM-EDX measurements, ICP-OES measurements, in situ resistance, anomalous scattering agreement factors, structure projection along <100>_p, low temperature magnetization, ex situ PXRD patterns of annealed samples, frequency dependent capacitance and dielectric loss, CBED whole pattern symmetry, magnetization loops (PDF)

Crystallographic data for GaFeO₃ (CIF)

■ AUTHOR INFORMATION

Corresponding Authors

*m.j.rosseinsky@liverpool.ac.uk

*j.b.claridge@liverpool.ac.uk

ORCID

Sanliang Ling: 0000-0003-1574-7476

Dmitry Batuk: 0000-0002-6384-6690

Matthew J. Rosseinsky: 0000-0002-1910-2483

Notes

The authors declare no competing financial interest.

■ ACKNOWLEDGMENTS

This work was funded by the EPSRC under EP/N004884. We thank the STFC for provision of beam time at ISIS and Diamond Light Source. We thank the Materials Chemistry Consortium (EPSRC, EP/L000202) for access to computer time on the ARCHER UK National Supercomputing Service

(<http://www.archer.ac.uk>). A.M.A. is grateful to the Russian Science Foundation (Grant 14-13-00680) for financial support. M.J.R. is a Royal Society Research Professor. We wish to thank Dr. Ming Li (University of Nottingham, UK) for helpful discussion and advice. Original data is available at the University of Liverpool's DataCat repository at DOI: 10.17638/datacat.liverpool.ac.uk/235. The supporting crystallographic information file may also be obtained from FIZ Karlsruhe, 76344 Eggenstein-Leopoldshafen, Germany (e-mail: crysdata@fiz-karlsruhe.de), on quoting the deposition number CSD-432419.

■ REFERENCES

- (1) Scott, J. F. *Nat. Mater.* **2007**, 6 (4), 256–257.
- (2) Bibes, M.; Barthelemy, A. *Nat. Mater.* **2008**, 7 (6), 425–426.
- (3) Hill, N. A. *J. Phys. Chem. B* **2000**, 104 (29), 6694–6709.
- (4) Hill, N. A.; Filippetti, A. *J. Magn. Magn. Mater.* **2002**, 242, 976–979.
- (5) Khomskii, D. I. *J. Magn. Magn. Mater.* **2006**, 306 (1), 1–8.
- (6) Sando, D.; Barthélémy, A.; Bibes, M. *J. Phys.: Condens. Matter* **2014**, 26 (47), 473201.
- (7) Catalan, G.; Scott, J. F. *Adv. Mater.* **2009**, 21 (24), 2463–2485.
- (8) Wang, J.; Neaton, J. B.; Zheng, H.; Nagarajan, V.; Ogale, S. B.; Liu, B.; Viehland, D.; Vaithyanathan, V.; Schlom, D. G.; Waghmare, U. V.; Spaldin, N. A.; Rabe, K. M.; Wuttig, M.; Ramesh, R. *Science* **2003**, 299 (5613), 1719–1722.
- (9) Heron, J. T.; Trassin, M.; Ashraf, K.; Gajek, M.; He, Q.; Yang, S. Y.; Nikonov, D. E.; Chu, Y. H.; Salahuddin, S.; Ramesh, R. *Phys. Rev. Lett.* **2011**, 107 (21), 1.
- (10) Mandal, P.; Pitcher, M. J.; Alaria, J.; Niu, H.; Borisov, P.; Stamenov, P.; Claridge, J. B.; Rosseinsky, M. *J. Nature* **2015**, 525 (7569), 363–366.
- (11) Benedek, N. A.; Fennie, C. J. *Phys. Rev. Lett.* **2011**, 106 (10), 1.
- (12) Pitcher, M. J.; Mandal, P.; Dyer, M. S.; Alaria, J.; Borisov, P.; Niu, H.; Claridge, J. B.; Rosseinsky, M. *J. Science* **2015**, 347 (6220), 420–424.
- (13) Alaria, J.; Borisov, P.; Dyer, M. S.; Manning, T. D.; Lepadatu, S.; Cain, M. G.; Mishina, E. D.; Sherstyuk, N. E.; Ilyin, N. A.; Hadermann, J.; Lederman, D.; Claridge, J. B.; Rosseinsky, M. *J. Chem. Sci.* **2014**, 5 (4), 1599–1610.
- (14) Li, M.-R.; Adem, U.; McMitchell, S. R. C.; Xu, Z.; Thomas, C. I.; Warren, J. E.; Giap, D. V.; Niu, H.; Wan, X.; Palgrave, R. G.; Schiffrmann, F.; Cora, F.; Slater, B.; Burnett, T. L.; Cain, M. G.; Abakumov, A. M.; van Tendeloo, G.; Thomas, M. F.; Rosseinsky, M. J.; Claridge, J. B. *J. Am. Chem. Soc.* **2012**, 134 (8), 3737–3747.
- (15) Li, M. R.; Walker, D.; Retuerto, M.; Sarkar, T.; Hadermann, J.; Stephens, P. W.; Croft, M.; Ignatov, A.; Grams, C. P.; Hemberger, J.; Nowik, I.; Halasyamani, P. S.; Tran, T. T.; Mukherjee, S.; Dasgupta, T. S.; Greenblatt, M. *Angew. Chem., Int. Ed.* **2013**, 52 (32), 8406–8410.
- (16) Li, M. R.; Stephens, P. W.; Retuerto, M.; Sarkar, T.; Grams, C. P.; Hemberger, J.; Croft, M. C.; Walker, D.; Greenblatt, M. *J. Am. Chem. Soc.* **2014**, 136 (24), 8508–8511.
- (17) Ye, M.; Vanderbilt, D. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2016**, 93 (13), 134303.
- (18) Kawamoto, T.; Fujita, K.; Yamada, I.; Matoba, T.; Kim, S. J.; Gao, P.; Pan, X.; Findlay, S. D.; Tassel, C.; Kageyama, H.; Studer, A. J.; Hester, J.; Irifune, T.; Akamatsu, H.; Tanaka, K. *J. Am. Chem. Soc.* **2014**, 136 (43), 15291–15299.
- (19) Bréard, Y.; Fjellvåg, H.; Hauback, B. *Solid State Commun.* **2011**, 151 (3), 223–226.
- (20) Sharma, K.; Reddy, V. R.; Gupta, A.; Kaushik, S. D.; Siruguri, V. *J. Phys.: Condens. Matter* **2012**, 24 (37), 1.
- (21) Uk Kang, K.; Baek Kim, S.; Yong An, S.; Cheong, S.-W.; Sung Kim, C. *J. Magn. Magn. Mater.* **2006**, 304 (2), e769–e771.
- (22) O'Dell, T. H. *Int. J. Magn.* **1973**, 4 (3), 239–244.
- (23) Arima, T.; Higashiyama, D.; Kaneko, Y.; He, J. P.; Goto, T.; Miyasaka, S.; Kimura, T.; Oikawa, K.; Kamiyama, T.; Kumai, R.;

Tokura, Y. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2004**, *70* (6), 064426.

(24) Fujita, K.; Kawamoto, T.; Yamada, I.; Hernandez, O.; Hayashi, N.; Akamatsu, H.; Lafargue-Dit-Hauret, W.; Rocquefelte, X.; Fukuzumi, M.; Manuel, P.; Studer, A. J.; Knee, C. S.; Tanaka, K. *Chem. Mater.* **2016**, *28* (18), 6644–6655.

(25) Arielly, R.; Xu, W. M.; Greenberg, E.; Rozenberg, G. K.; Pasternak, M. P.; Garbarino, G.; Clark, S.; Jeanloz, R. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2011**, *84* (9), 094109.

(26) Marezio, M.; Remeika, J. P. *J. Chem. Phys.* **1967**, *46* (5), 1862–1865.

(27) Bull, C. L.; Funnell, N. P.; Tucker, M. G.; Hull, S.; Francis, D. J.; Marshall, W. G. *High Pressure Res.* **2016**, *36*, 493–511.

(28) Klotz, S.; Le Godec, Y.; Straessle, T.; Stuhr, U. *Appl. Phys. Lett.* **2008**, *93* (9), 1.

(29) Zha, C.-S.; Mibe, K.; Bassett, W. A.; Tschauner, O.; Mao, H.-K.; Hemley, R. J. *J. Appl. Phys.* **2008**, *103* (5), 054908.

(30) Le Godec, Y.; Dove, M. T.; Francis, D. J.; Kohn, S. C.; Marshall, W. G.; Pawley, A. R.; Price, G. D.; Redfern, S. A. T.; Rhodes, N.; Ross, N. L.; Schofield, P. F.; Schooneveld, E.; Syfosse, G.; Tucker, M. G.; Welch, M. D. *Mineral. Mag.* **2001**, *65* (6), 737–748.

(31) Borisov, P.; Hochstrat, A.; Shvartsman, V. V.; Kleemann, W. *Rev. Sci. Instrum.* **2007**, *78* (10), 106105.

(32) VandeVondele, J.; Krack, M.; Mohamed, F.; Parrinello, M.; Chassaing, T.; Hutter, J. *Comput. Phys. Commun.* **2005**, *167* (2), 103–128.

(33) Hutter, J.; Iannuzzi, M.; Schiffmann, F.; VandeVondele, J. *Wiley Interdiscip. Rev.: Comput. Mol. Sci.* **2014**, *4* (1), 15–25.

(34) VandeVondele, J.; Hutter, J. *J. Chem. Phys.* **2007**, *127* (11), 114105–114105.

(35) Goedecker, S.; Teter, M.; Hutter, J. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1996**, *54* (3), 1703–1710.

(36) Krack, M. *Theor. Chem. Acc.* **2005**, *114* (1–3), 145–152.

(37) Adamo, C.; Barone, V. *J. Chem. Phys.* **1999**, *110* (13), 6158.

(38) Ernzerhof, M.; Scuseria, G. E. *J. Chem. Phys.* **1999**, *110* (11), 5029.

(39) Guidon, M.; Hutter, J.; VandeVondele, J. *J. Chem. Theory Comput.* **2010**, *6* (8), 2348–2364.

(40) Spencer, J.; Alavi, A. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2008**, *77* (19), 193110–193110.

(41) Pauling, L.; Hendricks, S. B. *J. Am. Chem. Soc.* **1925**, *47*, 781–790.

(42) Blake, R. L.; Hessevick, R. E.; Zoltai, T.; Finger, L. W. *Am. Mineral.* **1966**, *51* (1–2), 123–129.

(43) Buxton, B. F.; Eades, J. A.; Steeds, J. W.; Rackham, G. M. *Philos. Trans. R. Soc., A* **1976**, *281* (1301), 171–194.

(44) Wills, A. S. *Phys. B (Amsterdam, Neth.)* **2000**, *276*, 680–681.

(45) Shull, C. G.; Strauser, W. A.; Wollan, E. O. *Phys. Rev.* **1951**, *83* (2), 333–345.

(46) Capillas, C.; Tasci, E. S.; de la Flor, G.; Orobengoa, D.; Perez-Mato, J. M.; Aroyo, M. I. *Z. Kristallogr.* **2011**, *226* (2), 186–196.

(47) Murad, E. *Am. Mineral.* **1982**, *67* (9–10), 1007–1011.

(48) Forsyth, J. B.; Hedley, I. G.; Johnson, C. E. *J. Phys. C: Solid State Phys.* **1968**, *1* (1), 179–188.

(49) Schmid, H. *J. Phys.: Condens. Matter* **2008**, *20* (43), 434201.

(50) Perez-Mato, J. M.; Gallego, S. V.; Tasci, E. S.; Elcoro, L.; de la Flor, G.; Aroyo, M. I. *Annu. Rev. Mater. Res.* **2015**, *45*, 217–248.

(51) Mandal, P.; Pitcher, M. J.; Alaria, J.; Niu, H. J.; Zanella, M.; Claridge, J. B.; Rosseinsky, M. J. *Adv. Funct. Mater.* **2016**, *26* (15), 2523–2531.

(52) Mohamed, M. B.; Senyshyn, A.; Ehrenberg, H.; Fuess, H. J. *Alloys Compd.* **2010**, *492* (1–2), L20–L27.