

Determination of the crystal and magnetic structure of the DyCrO_4 -scheelite polymorph by neutron diffraction

This content has been downloaded from IOPscience. Please scroll down to see the full text.

2014 J. Phys.: Conf. Ser. 549 012021

(<http://iopscience.iop.org/1742-6596/549/1/012021>)

[View the table of contents for this issue](#), or go to the [journal homepage](#) for more

Download details:

IP Address: 189.218.98.177

This content was downloaded on 26/06/2016 at 08:52

Please note that [terms and conditions apply](#).

Determination of the crystal and magnetic structure of the DyCrO_4 -scheelite polymorph by neutron diffraction

A. J. Dos santos-García¹, E. Climent-Pascual¹, M. G. Rabie¹, J. Romero de Paz¹, J. M. Gallardo Amores¹, D. Khalyavin² and R. Sáez-Puche¹

¹Departamento de Química Inorgánica, Facultad de Químicas, Universidad Complutense de Madrid, 28040 Madrid, Spain.

²ISIS Facility, Rutherford Appleton Laboratory CCLRC, Chilton, Didcot, Oxfordshire OX11 0QX, United Kingdom

E-mail: rsp92@ucm.es

Abstract. Neutron diffraction data of DyCrO_4 oxide, prepared at 4 GPa and 833 K from the ambient pressure zircon-type, reveal that crystallize with the scheelite-type structure, space group $I4_1/a$. Accompanying this structural phase transition induced by pressure the magnetic properties change dramatically from ferromagnetism in the case of zircon to antiferromagnetism for the scheelite polymorph with a $T_N = 19$ K. The analysis of the neutron diffraction data obtained at 1.2 K has been used to determine the magnetic structure of this DyCrO_4 -scheelite oxide which can be described with a $\mathbf{k} = [0, 0, 0]$ as propagation vector, where the Dy and Cr moments are lying in the ab -plane of the scheelite structure. The ordered magnetic moments are $10 \mu_B$ and $1\mu_B$ for Dy^{+3} and Cr^{+5} respectively.

1. Introduction

Phase transitions induced by pressure have been studied for the zircon mineral ZrSiO_4 and the analogous zircon-types of RXO_4 ($\text{X} = \text{As}$ and V) which transform the tetragonal space group $I4_1/\text{amd}$ into a scheelite-type structure, space group $I4_1/a$. Recently for YbPO_4 and LuPO_4 , it was revealed using in-situ synchrotron x-ray diffraction experiments that the pressure-induced zircon-to-scheelite transition is reversible and the scheelite high-pressure phase cannot be quenched to ambient conditions in these phosphates [1]. In the case of vanadates and arsenates, this phase transition from zircon to scheelite, with an increase in the density of 11%, takes place at 8 GPa and 773 K [2, 3]. Regarding the high pressure phase transformations in RCrO_4 , in which we are interested, only few studies have been reported. This could be due to the high instability of Cr^{+5} and its tendency to be reduced to give the most stable distorted phase of perovskite RCrO_3 . However, it has been recently reported by our research group that zircon- RCrO_4 phases transform to a scheelite polymorph at 4 GPa and 813 K for the HoCrO_4 and TbCrO_4 compounds, which are quenchable after releasing the pressure [4, 5]. Accompanying this structural phase transition from zircon to scheelite the magnetic properties change dramatically. In this sense, most of the zircon-type RCrO_4 oxides being ferromagnetic become antiferromagnetic for the corresponding known scheelite polymorph. Detailed structural analysis by x-ray diffraction



Content from this work may be used under the terms of the [Creative Commons Attribution 3.0 licence](https://creativecommons.org/licenses/by/3.0/). Any further distribution of this work must maintain attribution to the author(s) and the title of the work, journal citation and DOI.

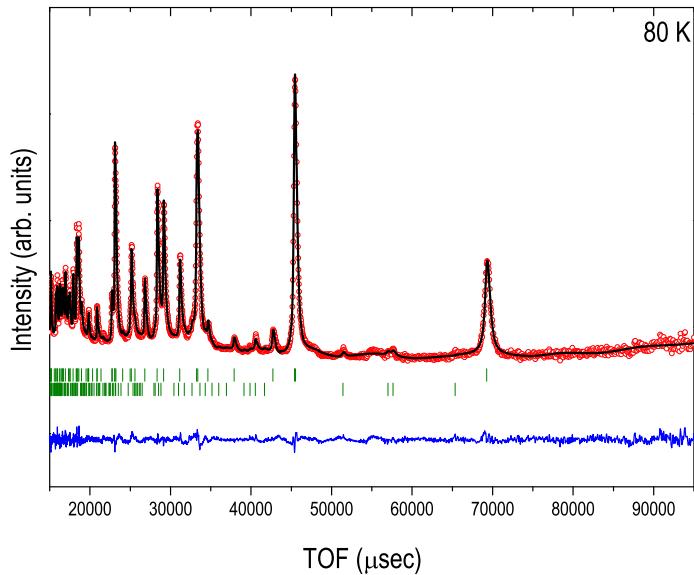


Figure 1. Rietveld refinement of the DyCrO_4 scheelite polymorph at 80 K for TOF neutron diffraction data. First raw of the vertical bars (i) corresponds to the DyCrO_4 scheelite. Second line (ii) is for DyCrO_3 distorted perovskite.

(XRD) and neutron diffraction (NPD) allow us to establish structure-magnetic properties relationships, which represents one of the main interests in the solid-state science. In this work, we aim to study the scheelite- DyCrO_4 oxide through investigating the structural and magnetic properties. Therefore, we focus first on the structural phase transition from the zircon-like to the scheelite-like structure under pressure and temperature. Second, we report the study of the magnetic properties of this DyCrO_4 from magnetization and neutron diffraction measurements.

2. Experimental

The DyCrO_4 zircon-phase sample, which was prepared by a precursor method described elsewhere, has been treated at 4 GPa and 833 K and 35-50 minutes in a CONAC-type press. DyCrO_4 scheelite oxide was first studied by X-ray powder diffraction using a Philips X'Celetor diffractometer with a primary beam monochromator consisting of a curved Ge (1 1 1) crystal aligned to obtain $\text{CuK}_{\alpha 1}$ radiation. A range of 2θ -angle between 10° and 90° was recorded with a step size of 0.0167° collected for 150s. Neutron diffraction experiments were done at the ISIS facility in the UK using the WISH cold-neutron time of flight (TOF) powder diffractometer. All obtained diffraction patterns were analyzed using the FullProf Suite Program. Magnetic susceptibility and magnetization measurements were performed in a SQUID Quantum Design MPS XL from 300 K to 2 K temperature range in different magnetic fields up to 5T.

3. Results and discussion

3.1. Structural characterization

The structure of the DyCrO_4 compound obtained after treating the DyCrO_4 -zircon polymorph at 4 GPa and 833 K has been refined from the X-ray and neutron diffraction data using the Rietveld method with the Fullprof program. As it is shown in Figure 1 the neutron diffraction data obtained at 80 K show the reflections conditions compatible with the space group $I4_1/a$ characteristic of the scheelite type structure.

The refined atomic positions are Dy at 4b (0, 1/4, 5/8), 4a (0, 1/4, 1/8) for Cr and the oxygen atoms are located at the 16f (x, y, z). The lattice parameters and main bond angles and interatomic distances are given in Table 1.

It is worth noting that small amount of impurities such as DyCrO_3 has also been included in the refinement, 8.98 (57) %. The zircon-type structure of RCrO_4 can be described as formed by

Table 1. Control sequences to describe lines and symbols in figure captions.

T (K)	80	1.2
a (Å)	5.0170(2)	5.0148(2)
b (Å)	11.3079(6)	11.3037(5)
V (Å ³)	284.62(2)	284.27(2)
U _{Dy} (Å ²)	0.0003(8)	0.0002
U _{Cr} (Å ²)	0.019(3)	0.0002
x _o	0.2437(5)	0.2437
y _o	0.6091(4)	0.6091
z _o	0.5486(2)	0.5486
U _o (Å ²)	0.0105(14)	0.0002(8)
d _{Cr-O} (Å)	1.7020(22) x 4	1.7020 x 4
d _{Dy-O} (Å)	2.3413(22) x 4	2.3413 x 4
	2.4177(23) x 4	2.4177 x 4
Cr - O - Dy (deg.)	121.759 (114)	121.759
	132.242(82)	132.242
μ _{xy,Dy} (μ _B)	—	9.67(10)
μ _{xy,Cr} (μ _B)	—	0.99(12)
R _{Bragg} (%)	2.44	5.49
R _p (%)	3.81	4.02
R _{wp} (%)	2.10	5.18
χ ²	2.62	1.32
Magnetic R-factor (%)	—	6.82

chains of CrO₄ and RO₈ polyhedra which are parallel to the c-axis and alternating by an edge sharing as seen in Figure 2a. Adjacent rods are connected along a and b-axis by zig-zag of edge sharing between RO₈ polyhedra. In case of the scheelite structure, CrO₄ distorted tetrahedra are aligned along the a-axis, while RO₈ bisdisphenoids are intercalated between the CrO₄ tetrahedra (Figure 2b).

The RO₈ polyhedra shares edges with adjacent RO₈ polyhedra and form along a-direction zig-zag chains, which are cross-linked by tetrahedra via corner-sharing (figure 2b). However, there is no edge-sharing between RO₈ and CrO₄ polyhedra. The difference in the tilting angle between different polyhedra, as well as in the packing after the transition provides an remarkable change in the Cr- O - R angles as it will be discussed later to explain the different magnetic behavior that presents this scheelite polymorph in comparison with the zircon one.

3.2. Magnetic properties

Figure 3 shows the evolution of the magnetic susceptibility with the temperature and it can be observed that the susceptibility obeys a Curie- Weiss behavior, $\chi = C/T + \theta$ in the temperature range 300 - 40 K, see Figure 3 inset.

It is also observed a small anomaly at 150 K due to the presence of the distorted perovskite DyCrO₃ that become antiferromagnetically ordered at this temperature with a small canting. However the presence of this phase doesn't affect to the magnetic properties of the scheelite-DyCrO₄ oxide. In this sense, the obtained magnetic moment takes the value of 11.2 μ_B which fairly agrees with the expected for this compound is 10.80 μ_B . The Weiss constant (θ) takes

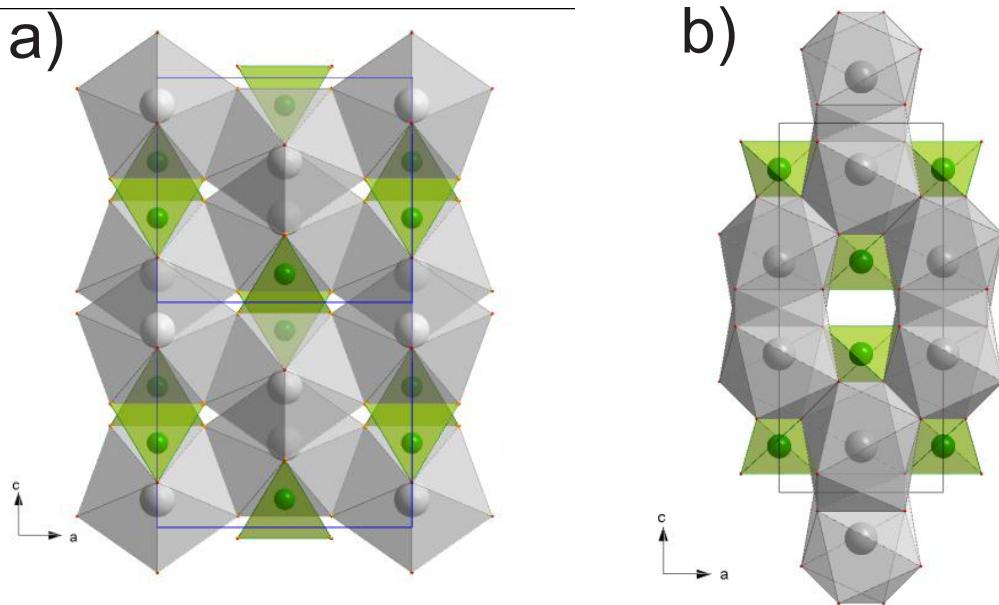


Figure 2. a) Crystal structure of the zircon-DyCrO₄ and b) scheelite-DyCrO₄ polymorph.

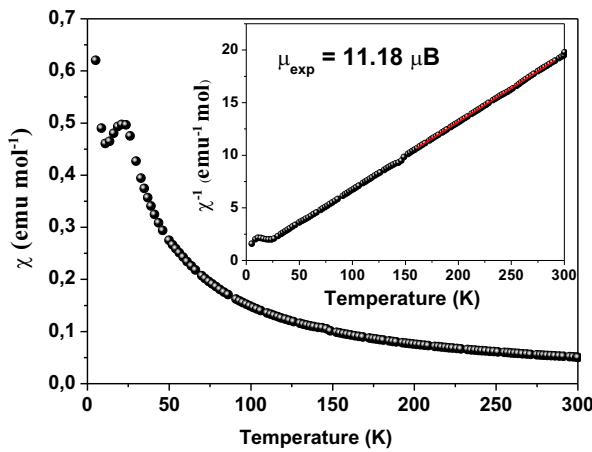


Figure 3. ZFC magnetization measurements for DyCrO₄ scheelite in a 0.05 T field. The inset shows the temperature dependence of the reciprocal susceptibility.

the value of -5.6 K which is indicative of the existence of antiferromagnetic interactions in this oxide. These interactions are fully confirmed the onset of a net maximum at 20 K in the χ vs T plot, see Figure 3. The increasing of the susceptibility below the T_N is due to presence of the small amount of impurities mentioned earlier. The different magnetic behavior that present both DyCrO₄ polymorphs, the scheelite form is antiferromagnetic, while the zircon-DyCrO₄ have been reported to be ferromagnetic [6] can be explained from the analysis of the structure of both polymorphs. As it was reported previously, these interactions take place through the superexchange Cr⁺⁵-O-Dy⁺³ pathway in which both Cr and Dy are involved. Since the Cr-O and Dy-O interatomic distances remain almost constant for both polymorph, the change in the sign of the exchange integral going from the zircon to scheelite form is mainly due to remarkable differences found in the Cr⁺⁵-O-Dy⁺³ bond angle found in both polymorphic phases. The magnetic structure of the DyCrO₄-scheelite polymorph has been determined from the analysis of the neutron diffraction data obtained at 1.2 K. The neutron powder diffraction patterns

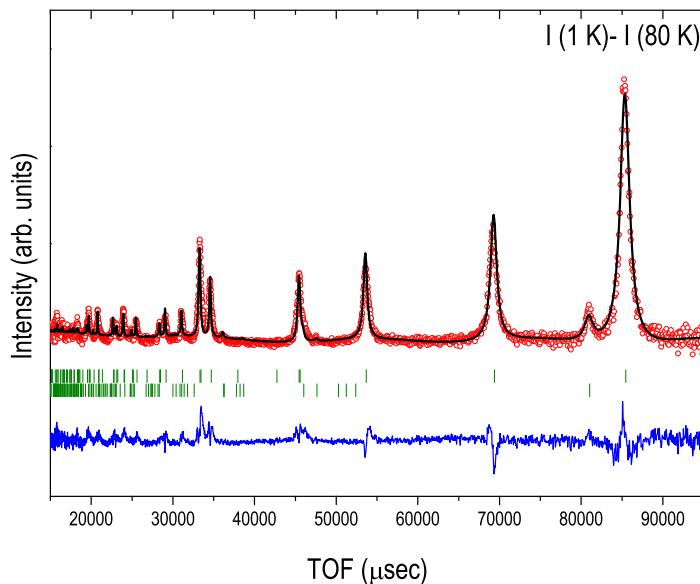


Figure 4. Magnetic structure fit from the difference between the 1.2 and 80 K neutron diffraction profiles of DyCrO_4 . First ticks of vertical marks (i) corresponds to the magnetic contribution from the DyCrO_4 scheelite and second line (ii), magnetic contribution from the DyCrO_3 distorted perovskite.

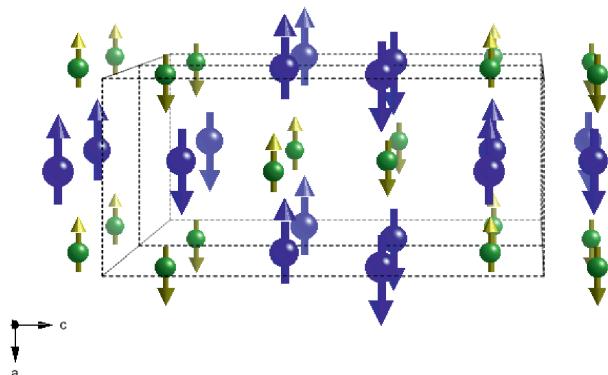


Figure 5. Magnetic structure of the DyCrO_4 scheelite. Blue and yellow arrows stem for the Dy and Cr magnetic moments respectively.

show the onset of new reflections forbidden for the space group $I4_1/a$ along with a progressive increase of certain reflections below $T_N = 20$ K. These magnetic reflections, see Figure 4, have been indexed on the basis of the coincidence between the crystal and magnetic cells, with the propagation vector $\mathbf{k} = [0, 0, 0]$.

The thermal evolution of the integrated intensity of the (002) and (110) magnetic reflections reveals that these magnetic reflections disappear at 22 K, a higher ordering temperature than the observed one from the magnetic susceptibility measurements. The magnetic structure is defined in the primitive $P1$ space group and the best agreement ($\text{RM} = 0.068$) between the experimental and calculated neutron diffraction profiles was obtained when Cr^{+5} and Dy^{+3} magnetic moments are aligned parallel to the ab-plane in the same manner like for GdCrO_4 scheelite [7], see Figure 5.

The saturation magnetic moments obtained from the Rietveld refinement are $9.67(10)\mu_B$ and $0.99(12)\mu_B$ for Dy^{+3} and Cr^{+5} respectively. As it can be observed in Figure 5 the magnetic moments of Dy^{+3} are antiferromagnetically coupled between the $(\text{Dy}_2\text{O}_{14})$ dimers resulting from the two (DyO_8) bisdiphenoids sharing a edge in the ab-plane of the scheelite structure. The Cr^{+5} moments are also antiferromagnetically coupled in the ab-plane of the structure given as

result the collinear magnetic structure depicted in Figure 5.

4. Acknowledgments

The authors acknowledge funding from Comunidad de Madrid under the research project S-2009/PPQ-1626 and MICINN through MAT2010-19460. AJD is grateful to MICINN and UCM for a Juan de la Cierva contract (JCI-2012-08229). M. Rabie is also grateful to financial support for a pre-doctoral grant under research SOPRANO-Marie Curie actions (FP7/20072013 under Grant Agreement no.214040). Authors are also indebted to ISIS-facility for beamtime allocation at WISH instrument and Dr. L. C. Chapon and Dr. P. Manuel for valuable comments.

5. References

- [1] Zhang F, Lang M, Ewing R, Lian J, Wang Z, Hu J and Boatner L 2008 *Journal of Solid State Chemistry* **181** 2633 – 2638
- [2] Duclos S J, Jayaraman A, Espinosa G, Cooper A and Sr R M 1989 *Journal of Physics and Chemistry of Solids* **50** 769 – 775
- [3] Stubican V S and Roy R 1963 *Journal of Applied Physics* **34** 1888–1890
- [4] Climent-Pascual E, de Paz J R, Gallardo-Amores J M and Sez-Puche R 2007 *Solid State Sciences* **9** 574 – 579
- [5] Climent E, Gallardo J, de Paz J R, Taira N and Puche R S 2009 *Journal of Alloys and Compounds* **488** 524 – 527
- [6] Long Y, Liu Q, Lv Y, Yu R and Jin C 2011 *Phys. Rev. B* **83**(2) 024416
- [7] Dos Santos-García A J, Climent-Pascual E, Gallardo-Amores J M, Rabie M G, Doi Y, de Paz J R, Beuneu B and Saez-Puche R 2012 *Journal of Solid State Chemistry* **194** 119 – 126